



Csire, G., Cserti, J., Tütto, I., & Újfalussy, B. (2016). Prediction of superconducting transition temperatures of heterostructures based on the quasiparticle spectrum. *Physical Review B*, 94(10), Article 104511. <https://doi.org/10.1103/PhysRevB.94.104511>

Publisher's PDF, also known as Version of record

Link to published version (if available):  
[10.1103/PhysRevB.94.104511](https://doi.org/10.1103/PhysRevB.94.104511)

[Link to publication record on the Bristol Research Portal](#)  
PDF-document

This is the final published version of the article (version of record). It first appeared online via APS at <https://doi.org/10.1103/PhysRevB.94.104511>. Please refer to any applicable terms of use of the publisher.

## University of Bristol – Bristol Research Portal

### General rights

This document is made available in accordance with publisher policies. Please cite only the published version using the reference above. Full terms of use are available: <http://www.bristol.ac.uk/red/research-policy/pure/user-guides/brp-terms/>

## Prediction of superconducting transition temperatures of heterostructures based on the quasiparticle spectrum

Gábor Csire,<sup>1,2</sup> József Cserti,<sup>2</sup> István Tüttő,<sup>1</sup> and Balázs Újfalussy<sup>1</sup>

<sup>1</sup>*Institute for Solid State Physics and Optics, Wigner Research Centre for Physics, Hungarian Academy of Sciences, P.O. Box 49, H-1525 Budapest, Hungary*

<sup>2</sup>*Department of Physics of Complex Systems, Eötvös University, Pázmány Péter sétány 1/A, H-1117 Budapest, Hungary*

(Received 22 March 2016; revised manuscript received 22 August 2016; published 14 September 2016)

In this paper we present material specific calculations of superconductor–normal metal heterostructures using density functional theory combined with a semiphenomenological parametrization of the electron-phonon coupling. In particular, we calculate the quasiparticle spectrum of different normal metal overlayers on a Nb(100) host. We find that the Andreev reflection leads to the formation of momentum dependent quasiparticle bands in the normal metal. As a consequence, the spectrum has a strongly momentum dependent induced gap. We develop a model to calculate the superconducting critical temperature from the thickness dependence of the induced gap. In the case of Au/Nb(100) heterostructures we find very good agreement with experiments. Moreover, predictions are made for similar heterostructures of other compounds.

DOI: [10.1103/PhysRevB.94.104511](https://doi.org/10.1103/PhysRevB.94.104511)

The experiments of Yamazaki *et al.* [1,2] pose a great challenge to the theory of superconductivity. In these experiments they studied the critical temperature of a very thin layer of gold grown on top of a thicker Nb host. While the thickness of the Nb sample (288 Å) was in the order of the superconducting coherence length (380 Å), the gold overlayer was only a couple of atomic layers thick. It was found that the superconducting transition temperature is significantly lowered in this composite compared to the bulk, and it decays monotonically as the thickness of the gold overlayer increases. While this appears to be a plausible consequence at first sight, it is surprising that the entire composite is superconducting. The explanation of these experimental findings based on the standard theory of superconductivity is very difficult, because within the BCS (Bardeen-Cooper-Schrieffer) theory [3] it is not easy to describe inhomogeneous systems. However, such systems can be treated efficiently in terms of the Bogoliubov–de Gennes (BdG) equations [4,5], especially when they are reformulated within the framework of density functional theory [6–10] leading to the so-called Kohn-Sham–Bogoliubov–de Gennes (KS–BdG) equations. In principle these equations are able to describe systems with inhomogeneities in the pairing potential.

In inhomogeneous systems, such as multilayers, it is expected that the Andreev reflection [11,12] leads to the formation of certain bound states, often referred to as Andreev bound states. Our main aim in this paper is to calculate the dispersion relation of Andreev states. We also verify that this effect enables the transport of supercurrents through nonsuperconducting materials, and is the key to predict the superconducting transition temperature in the whole system.

In what follows we numerically solve the KS–BdG equations, as was described in Ref. [10], for an Au/Nb(100) overlayer system. For varying Au thicknesses we calculate the quasiparticle electronic structure and obtain the superconducting gap for each thickness. Finally a method is developed to calculate the critical temperature from the gap and applied to several overlayer systems with different material constituents.

The first step down this road is to construct a realistic model of the interface lattice structure. Such a model can be built up from two-dimensional translational invariant atomic

layers as follows. We divide the system into three regions: (i) a semi-infinite bulk (Nb); (ii) the interface region that—in our case—consists of six superconducting layers (Nb), various numbers of normal metal layers and three layers of empty spheres; and (iii) a semi-infinite vacuum. This division of space is typical in screened Korringa-Kohn-Rostoker (KKR) [13] calculations in overlayer systems. Since the setup described in the experiment of Yamazaki *et al.* [1,2] is beyond our computational capability, we model the effect of a thick superconducting film by a semi-infinite bulk. Although the thickness of the Nb layers in the experiment is not strictly semi-infinite, it is thick enough to be approximated by a semi-infinite bulk system. We use six Nb layers to mimic the transition between the semi-infinite bulk and the overlayer. The Nb has the body-centered cubic (bcc) crystal structure with a lattice parameter of  $a = 3.3$  Å. We assumed the realistic face-centered cubic (fcc) crystal structure for the gold overlayers, and the termination of the material layers were modeled by a semi-infinite vacuum. We also neglected imperfections at the interface, such as interlayer relaxations and intermixing.

In such systems, where translational invariance is preserved only parallel to the interface, the quasiparticle spectrum is obtained as a function of a two-dimensional momentum vector  $\vec{k}_{\parallel}$ . To visualize this spectrum, it is customary to calculate the Bloch spectral function (BSF). In two-dimensionally translational invariant systems the BSF for layer  $I$  is defined as  $A_B^I(\varepsilon, \vec{k}_{\parallel}) = -\frac{1}{\pi} \text{Im} G_{II}(\varepsilon, \vec{k}_{\parallel})$ , where  $G_{II}$  is the layer projected Green's function (see Ref. [10]). Since the BSF is equivalent to the quasiparticle spectrum, drawing a contour plot of the BSF as a function of energy along specified directions of  $\vec{k}_{\parallel}$  is a powerful tool to visualize the quasiparticle states. Evidently, in a layered system this contour plot can be done for each layer.

In order to understand the quasiparticle spectrum in the superconducting state better, first we performed first-principles calculations just in the normal state, by simply solving the screened KKR equations [13] for the Au/Nb(001) overlayer system. In Fig. 1 we show the contour plot of the BSF for a layer that we considered to be in the “middle” of the samples of various Au layer thicknesses. The plots are restricted in

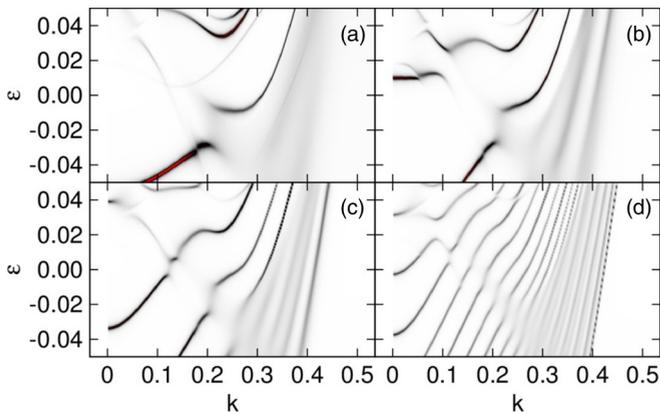


FIG. 1. Contour plot of the spectral function of Au/Nb(001) (normal state band structure) from the “middle” of the gold layers for different thicknesses of the gold: three Au layers (a), six Au layers (b), nine Au layers (c), and 24 Au layers (d).

energy to the range of  $[-0.05 \text{ Ry}, 0.05 \text{ Ry}]$  (later we will choose  $\Delta_{\text{Nb}}$ , the superconducting gap to equal this value, and solve the BdG equations within this energy range). It can be seen from Fig. 1 that for energies where the density of states (DOS) in the bulk Nb is low, the states in the Au are confined, as they cannot scatter into the Nb, and on the other side the system is limited by vacuum. In regions where the DOS is high in the Nb, the states in the Au are smeared out, as here the electrons can scatter more easily into the other side of the interface. The confined states in the Au can be regarded as quantum-well (QW) states.

Now let us consider the Nb in the superconducting state and solve the first-principles BdG equations as described in Ref. [10]. In this formalism each layer is characterized by an additional, potential-like parameter, the superconducting gap  $\Delta$ . To solve the BdG equation we assumed that all Nb layers show the same superconducting gap  $\Delta_{\text{Nb}} = 0.05 \text{ Ry}$ . This is a much larger value than the gap observed experimentally [14], in order to make it easier to visualize the quasiparticle spectrum. Later, when we will calculate the superconducting transition temperature, we will repeat the calculation for a more realistic  $\Delta$ . We also assumed that the superconducting gap is zero in the Au layers, namely, we set  $\Delta_{\text{Au}} = 0.0 \text{ Ry}$ , as Au is not superconducting at all in the bulk.

Based on the symmetry of the BdG equations [5] it is known that in bulk superconductors the quasiparticle states can be obtained from the electronic states by mirroring the band structure of the normal state to the Fermi energy and opening up a gap. In the case of the Au/Nb(100) overlayer system the situation is entirely different, because the system is described by an inhomogeneous  $\Delta$  which, additionally, equals to zero in some layers. Therefore the main question is how the niobium host affects the quasiparticle spectrum of the gold overlayers. In Fig. 2 we plot the BSF summed up for all Au layers in the case of different total numbers of gold layers (right-hand side of the figure). To illustrate the role of the crystal structure, on the left-hand side of the figure we also show results of the same calculations performed by assuming bcc Au layers throughout the overlayer. This is not entirely unrealistic for very thin layers but most likely artificial for thicker ones, where the Au layers

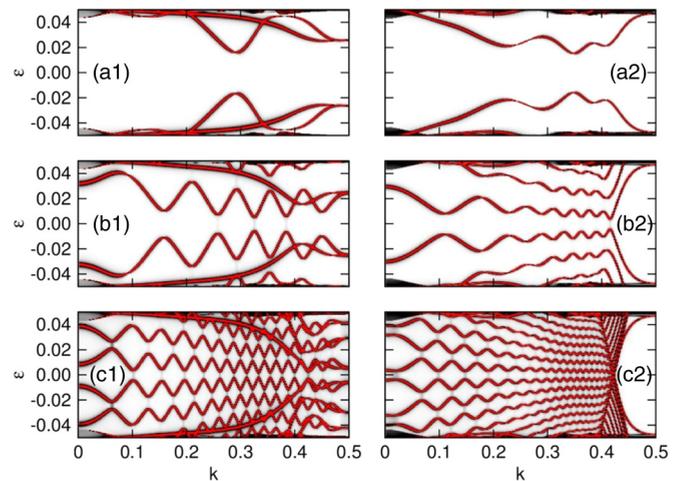


FIG. 2. Contour plot of the BSF summed up for all Au layers of Au/Nb(001) in the case of different thicknesses of the Au: three bcc Au layers (a1), nine bcc Au layers (b1), 24 bcc Au layers (c1), and three fcc Au layers (a2), nine fcc Au layers (b2), 24 fcc Au layers (c2). The momentum vector  $k$  is shown along the  $k_x = k_y$  line in the 2D Brillouin zone.

most certainly grow in an fcc structure. Unfortunately there is very little known of the crystal structures of thin Au layers on Nb.

By comparing Figs. 1(a), 1(c), 1(d) and Figs. 2(a2), 2(b2), 2(c2), we can immediately conclude that the proximity of a superconductor in the studied heterostructures induces the expected mirroring of the electronic bands within the energy range of the Nb gap, and additionally opens up a smaller gap at each band crossing. Although it is quite trivial, it is much easier to see the effect first in the case of the bcc Au, fully described in [10]. One can also see from the figure that the size of the induced gaps in the gold is strongly  $k_{\parallel}$  dependent, however—around the Fermi energy—it is the same for all layers, and it decreases as a function of the overall thickness of the gold overlayers. It should be noted as well that those regions of the spectrum which were more or less smeared out in the normal state (visualized in the figure by weaker lines) now sharpened up. This is the consequence of the opening of the superconducting gap in the Nb: the states where scattering into—on the other side of the interface—was allowed before, now disappeared because of the gap. We can also conclude from the figure that the quantum-well states, which we found to exist in the normal state band structure calculations, become bound Andreev states originating from the Andreev scattering at the interface. Finally, since Fig. 2 was obtained by summing up  $A_B^I(\varepsilon, \vec{k}_{\parallel})$ , and this sum does not show any significant broadening, it is clear that the quasiparticle spectrum is virtually identical in every interfacial layer. In Fig. 2 one can also observe changes in the quasiparticle spectrum owing to different lattice structures. In particular, more “oscillations” can be seen in fcc gold overlayers compared to the bcc ones, which is the consequence of more bands of the fcc gold in the normal state.

We are now ready to calculate the superconducting transition temperature  $T_c$ . In the strong-coupling limit (e.g., in the case of Nb) the  $T_c$  is given by the McMillan

formula [15,16]

$$T_c = \frac{\Theta_D}{1.45} \exp\left(-\frac{1.04(1 + \lambda_{\text{eff}})}{\lambda_{\text{eff}} - \mu^*(1 + 0.62\lambda_{\text{eff}})}\right), \quad (1)$$

where  $\Theta_D$  is the Debye temperature, and  $\mu^*$  is the dimensionless Coulomb pseudopotential which describes the effect of the Coulomb repulsion. For these two parameters we may assume the bulk values [1], justified by the fact that the niobium host is rather thick. The parameter  $\lambda_{\text{eff}}$  is an effective coupling parameter for the whole system. Following the argument of de Gennes [2,17] the simplest way to define such an effective interaction parameter in an inhomogeneous system is described by an averaging process in the following way. Let us interpret  $D_{\text{Au}}(\varepsilon_F)t_{\text{Au}}/[D_{\text{Nb}}(\varepsilon_F)t_{\text{Nb}} + D_{\text{Au}}(\varepsilon_F)t_{\text{Au}}]$  as a probability of finding an electron in the normal metal layers (Au) and  $D_{\text{Nb}}(\varepsilon_F)t_{\text{Nb}}/[D_{\text{Nb}}(\varepsilon_F)t_{\text{Nb}} + D_{\text{Au}}(\varepsilon_F)t_{\text{Au}}]$  in the superconducting Nb layers. Then the effective coupling  $\lambda_{\text{eff}}$  can be defined as

$$\lambda_{\text{eff}} = \frac{\lambda_{\text{Nb}}D_{\text{Nb}}(\varepsilon_F)t_{\text{Nb}} + \lambda_{\text{Au}}D_{\text{Au}}(\varepsilon_F)t_{\text{Au}}}{D_{\text{Nb}}(\varepsilon_F)t_{\text{Nb}} + D_{\text{Au}}(\varepsilon_F)t_{\text{Au}}}, \quad (2)$$

where  $t_{\text{Nb}}$  and  $t_{\text{Au}}$  are the thickness of the Nb and Au layers, respectively,  $\lambda_{\text{Nb}}$  is the electron-phonon coupling in the niobium, and  $D(\varepsilon_F)$  is the density of states at the Fermi level. While the density of states for the Nb can be approximated by the bulk value, the density of states in the gold should be defined as a layer average,  $D_{\text{Au}}(\varepsilon_F) = 1/N \sum_{l=1}^N D_{\text{Au}}^l(\varepsilon_F)$ , where  $N$  is the number of the gold overlayers. Since the whole niobium-gold system is superconducting (a common  $T_c$  obtained experimentally in Refs. [1,2]), Cooper pairs must exist throughout the whole system. Therefore, the existence of the superconducting gap in the Au layers can be viewed in a way that the proximity of the superconductor induces an effective coupling ( $\lambda_{\text{Au}}$ ) in the gold, which in turn can be obtained from the induced gap  $\Delta'_{\text{Au}}$  according to the BCS gap equation:

$$\lambda_{\text{Au}} = -\frac{1}{\log\left(\frac{\Delta'_{\text{Au}}}{2\hbar\omega_D^{\text{Nb}}}\right)}. \quad (3)$$

This induced gap  $\Delta'_{\text{Au}}$  can be read off from the quasiparticle spectrum, for which the whole calculation of the quasiparticle spectrum needs to be repeated with a more realistic value for  $\Delta_{\text{Nb}}$ , as we mentioned earlier. (For better visualization we used an artificially large  $\Delta_{\text{Nb}}$  in Fig. 2.) While the BCS theory is adequate only in the weak-coupling limit, nevertheless we still argue that the BCS gap equation may be applied here to the gold layers, since the induced gap is much smaller than the gap in the Nb. Although the BCS theory is valid for bulk systems, its applicability in the gold is motivated by the similarity of the layer resolved quasiparticle spectrums and the layer independent feature of the induced gap for a given thickness. To obtain the induced gap, we always take the maximum of the induced gap around the Fermi energy (as a function of  $\vec{k}_{\parallel}$ ) in the two-dimensional (2D) Brillouin zone because it is the most characteristic of the strength of the induced interaction in the gold. In summary, the  $\Delta'_{\text{Au}}$  induced gap can be read off from the calculated quasiparticle spectrum as the function of the thickness of the gold overlayers (see Fig. 3 inset), and the critical temperature can be calculated from the

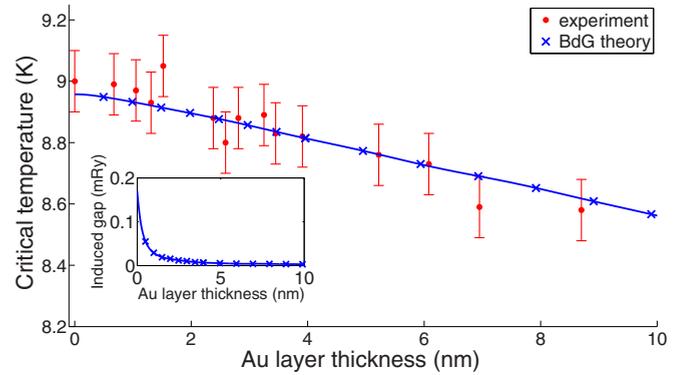


FIG. 3. The critical temperature as a function of the thickness of the gold obtained from the McMillan formula. The points with the error bars are the experimental results from Ref. [2]. The inset plot shows the induced gap on the gold layers as a function of the thickness of the gold.

McMillan formula given by Eq. (1). Figure 3 shows the critical temperature as a function of the thickness of the Au overlayers obtained from the procedure described above together with the experimental results taken from the papers [1,2]. One can clearly see that our theoretical results are in very good agreement with the experimental findings; all points are within the experimental errors. Moreover, the slow decrease of the critical temperature as a function of the Au overlayer thickness is well reproduced. We should emphasize that our theory contains only one parameter, namely, the critical temperature for the thick niobium slab. While in principle this quantity can be calculated [18], it is quite cumbersome. Therefore, for simplicity, here we take its experimental value. Consequently our calculation is not entirely first principles.

The theory presented in this paper so far can be applied without changes to other overlayer systems such as NbAg, NbIr, NbAl, and NbMo. Nevertheless, it should be mentioned, that many of the properties of the quasiparticle spectrum we studied above are connected to the fact that QW states form in the Au in the normal state. The formation of QW states, however, cannot be regarded as a universal feature of every overlayer on Nb. This is illustrated in Fig. 4, where we show

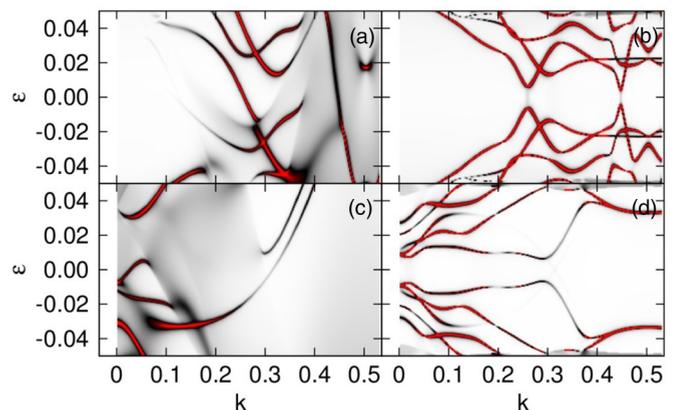


FIG. 4. Contour plot of the spectral function from the “middle” of the three overlayers: (a) Al/Nb(001) (normal state band structure) and (b) Al/Nb(001) (quasiparticle spectrum); (c) Mo/Nb(001) (normal state band structure) and (d) Mo/Nb(001) (quasiparticle spectrum).

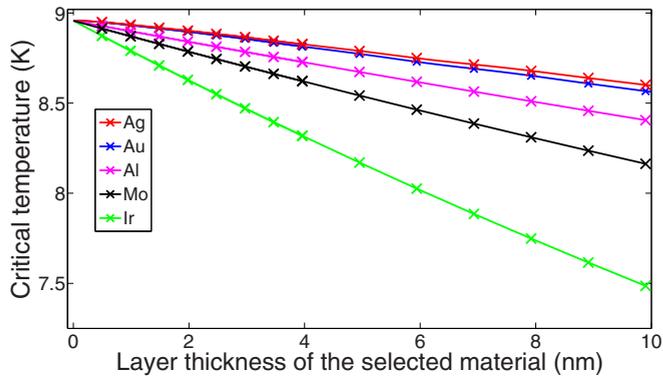


FIG. 5. The critical temperature as a function of the thickness in the case of different metal overlayers.

the normal state band structure and also the corresponding quasiparticle spectrum of Al and Mo overlayers on the Nb host. While there may be some quantum confinement present in these materials in the normal state, it is not as clearly exhibited as in the case of Au overlayers. It is clearly seen, that quantum confinement is still present in the superconducting state. It is important to notice as well, that in these systems it is hard to recognize how the quasiparticle spectrum could be obtained from the normal state band structure, as we mentioned before, based on the symmetry properties of the BdG equations. The most important feature of these plots is that in the superconducting state the induced gap around the Fermi level can still be observed, therefore the superconducting transition temperature can be predicted similarly to the NbAu heterostructure. This is shown in Fig. 5 for several overlayer systems.

It can be seen that it is a general trend that the superconducting transition temperature decays as the normal metal thickness increases, only the rate of the decay depends on the material of the overlayer. This behavior is a consequence of the size of the induced gap in the normal metal and also the change of the density of states at the Fermi level which enters the McMillan formula through the effective coupling parameter. This is most pronounced for the case of iridium overlayers, where the decay of the transition temperature is the fastest, mostly due to the much higher density of states at the Fermi level. We also found that our procedure to calculate the critical temperatures are rather robust regarding errors in the niobium's superconducting gap. Changes in  $\Delta_{\text{Nb}}$  less than 10%, causes changes in the critical temperature, which are definitely smaller than the experimental error [1].

In summary, we have investigated the quasiparticle spectrum, and the superconducting transition temperature of superconductor–normal metal heterostructures. We have developed a semiphenomenological method to predict the transition temperature of such heterostructures based on the solution of the KS–BdG equations. In the case of the Nb/Au(100) system we obtained very good agreement with the experimental findings. The theory was also applied for different metallic overlayers on a Nb host to predict the superconducting transition temperature.

This work was supported by the Hungarian National, Research, Development and Innovation Office under Contracts No. K115632 and No. K108676.

- 
- [1] H. Yamazaki, N. Shannon, and H. Takagi, *Phys. Rev. B* **73**, 094507 (2006).
- [2] H. Yamazaki, N. Shannon, and H. Takagi, *Phys. Rev. B* **81**, 094503 (2010).
- [3] J. Bardeen, L. N. Cooper, and J. R. Schrieffer, *Phys. Rev.* **108**, 1175 (1957).
- [4] N. N. Bogoliubov, *JETP USSR* **34**, 58 (1958).
- [5] P. G. de Gennes, *Superconductivity of Metals and Alloys* (W. A. Benjamin, New York, 1966).
- [6] L. N. Oliveira, E. K. U. Gross, and W. Kohn, *Phys. Rev. Lett.* **60**, 2430 (1988).
- [7] M. B. Suvasini, W. M. Temmerman, and B. L. Györfy, *Phys. Rev. B* **48**, 1202 (1993).
- [8] M. Lüders, M. A. L. Marques, N. N. Lathiotakis, A. Floris, G. Profeta, L. Fast, A. Continenza, S. Massidda, and E. K. U. Gross, *Phys. Rev. B* **72**, 024545 (2005).
- [9] M. A. L. Marques, M. Lüders, N. N. Lathiotakis, G. Profeta, A. Floris, L. Fast, A. Continenza, E. K. U. Gross, and S. Massidda, *Phys. Rev. B* **72**, 024546 (2005).
- [10] G. Csire, B. Újfalussy, J. Cserti, and B. Györfy, *Phys. Rev. B* **91**, 165142 (2015).
- [11] A. F. Andreev, *Sov. Phys. JETP* **19**, 1228 (1964).
- [12] G. E. Blonder, M. Tinkham, and T. M. Klapwijk, *Phys. Rev. B* **25**, 4515 (1982).
- [13] L. Szunyogh, B. Újfalussy, P. Weinberger, and J. Kollár, *Phys. Rev. B* **49**, 2721 (1994).
- [14] A. V. Pronin, M. Dressel, A. Pimenov, A. Loidl, I. V. Roshchin, and L. H. Greene, *Phys. Rev. B* **57**, 14416 (1998).
- [15] W. L. McMillan, *Phys. Rev.* **167**, 331 (1968).
- [16] P. B. Allen and R. C. Dynes, *Phys. Rev. B* **12**, 905 (1975).
- [17] P. G. De Gennes, *Rev. Mod. Phys.* **36**, 225 (1964).
- [18] B. M. Klein and D. A. Papaconstantopoulos, *Phys. Rev. Lett.* **32**, 1193 (1974).